Load ring weldable suits 90°-corners > VRBK-FIX <

Safety instructions

This safety instruction/declaration has to be kept on file for the whole lifetime of the product. Translation of the original safety instruction



RUD Ketten Rieger & Dietz GmbH u. Co. KG 73428 Aalen Tel. +49 7361 504-1370 Fax +49 7361 504-1171 sling@rud.com www.rud.com



Load ring for 90°-corners (weldable) VRBK-FIX

claration of conformity
Directive 2006/42/EC, annex II A and amendments
on Dietz GmbH u. Co. KG
Id by us because of its design and construction, appropriate, basic requirements of safety and y Directive 2006/42/EC as well as to the below is as well as technical specifications. ent, not being agreed upon with us, this declara-
BK-fix / VRBS / VRBG / VRBK / VRBSS
ed: : 2009-03 DIN EN ISO 12100 : 2011-03
he declaration documents: der, RUD Ketten, 73432 Aalen <u>e Kriegsmann,(Prokurist/QMB)</u> n and signature of the responsible person

RUD-Art.-Nr.: 7902520-EN / 10.017



Before initial usage of the RUD-VRBK-FIX, please read carefully the safety instruc-

tions. Make sure that you have understood all subjected matters.

Non-observance can lead to serious personal injuries and material damage and eliminates warranty.

1 Safety instructions

ATTENTION

Wrong positioned or damaged weld-on lifting points as well as improper use can lead to injuries of persons and damage at property, when load falls down. Please check all lifting points carefully before every usage.

RUD-Ilifting points VRBK-FIX must only be used by instructed and competent persons considering BGR 500 / DGUV 100-500, and outside Germany noticing the country specific statutory regulations.

2 Intended use of the VRBK-FIX

RUD-Lifting points VRBS-FIX must only be used for the assembly at the load or at lifting means.

They are designed and intented to attach lifting means.

RUD Lifting points can also be used as lashing points to attach lashing means.

RUD-lifting points must only be used in the hereby specified case of operation.

3 Assembly- and instruction manual

3.1 General information

- Capability of temperature usage: When used at higher temperatures the working load limit (WLL) of the lifting point must be reduced as follows:
 - -20°C up to 200°C no reduction
 - 200°C up to 300°C minus 10 %
 - 300°C up to 400°C minus 25 %

Temperatures exceeding 400°C are prohibited!

- RUD-lifting points VRBK-FIX must not be used with aggressive chemicals such as acids, alkaline solutions and their vapours.
- Please mark mounting position of lifting point with a coloured contrast paint for better visibility.


- VRBK-FIX will be delivered with a pink powder coated lifting ring.
- VRBS-FIX includes a protected positioned clamping spring, inside the weld-on block. The spring holds the weld-on blocks together with the ring and creates at the same time a radial clamping function.
- VRBK-FIX will be delivered as a complete assembled unit.

3.2 Hints for the assembly

Basically essential:

- The material construction to which the lashing point will be attached should be of adequate strength to withstand forces during lifting without deformation. The weld-on material must be suitable for welding and the contact areas must be free from dirt, oil, colour, ect. The material of the forged welding block is: S355J2+N (1.0577+N (St52-3))
- The position of the lifting points must be carried out in such a way that unintended movement like turning or flipping will be avoided.
 - For single leg lifts, the lifting point should be vertically above the centre of gravity of the load
 - For two leg lifts, the lifting points must be equidistant to/or above the centre of gravity of the load.
 - For three and four leg lifts, the lifting points should be arranged symmetrical around the centre of gravity, in the same plane if possible.
- · Load symmetry:

Determine the necessary WLL of each lifting point for a symmetrical load by using the following physical calculation formula:



W_{LL} = necessary WLL of lifting point / single strand (kg) G = weight of load (kg) n = number of load bearing strands

= number of	load bearing strands
= inclination a	angle of single stra

Number of load bearing strands:

	Symmetric	Unsymmetric
two leg	2	1
three / four le	a 3	1

Chart 1: Load bearing strands (compare to chart 2)

• Check finally the correct assembly (see chapter 4, Inspection criteria).

3.3 Hints for the welding


The welding should only be carried out according to DIN EN ISO 9606-1 or AWS Standards by an authorized and certified welder.

Verification of the used weld-on material must be checked with the supplier of the welding electrodes.

HINTS

 Never weld at the quenched and tempered ring!

- Weld all seams at the same temperature.
- 1. Check before initial appending of the VRBK-FIX, the position of the weld-on blocks to each other, that means the base area must be at the same level.
- 2. Append weld-on blocks.
- Check function of the ring. The ring must be able to pivot 270°. If necessary please correct.
- 4. Once appending and checking of the function have been carried please finish the root run. The outside positioned weld layers must be carried out first. The described welding sequences must be observed compulsive.
- 5. Begin at starting point S1 and weld subsequently the sections 1-4 (Picture 1).
- 6. Then weld the opposite side identically (starting point S2 and chapter 5-8).
- 7. Afterwards close the rot pass at the inside areas. (chapter 9-10 and 11-12)

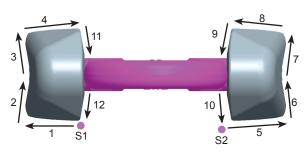


Pic. 1: Welding sequence of the root run (S=Starting point

- 8. Finally please let the parts cool down.
- 9 Remove any welding mistakes and dirt at the root weld before applying the cover weld seams.
- 10.Subsequently please weld the closure welds. Start at the inside. The described welding sequences must be observed compulsive. Chose type and dimension of weld seam from picture 3 and chart 4.
- 11.Begin at starting point S3 and weld subsequently the chapters 1-6 (picture 2)
- 12.Please weld then the opposite side identically. (tarting point S4 and chapter 7-12)



HINT

Please adhere the requested weld seam thickness in any cases. Any change can result in a malfulction of the ring latch.

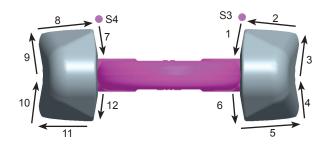


Pic. 2: Sequence of closure welding (S=Starting point)

13.Please check by a competent person after welding the ongoing usage of the weld-on lifting point (see chapter 4, Inspection criteria).



HINT:

By the position of the weld-seam (HY-weld circumferential) the following requirements will be observed: DIN 18800 steel constructions requires: at outdoor buildings or when strong corrosion must be expected weld seams must be carried out as continuous fillet weld seams.

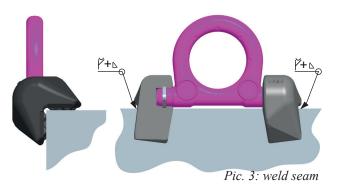

3.4 User instruction


• Check frequently and before each initial operation the whole lashing point in regard of linger ability as a lifting mean, regarding corrosion, wear, deformation etc. (see chapter 4, Inspection criteria).



ATTENTION Wrong positioned or damaged weld-on lifting points as well as improper use can lead to injuries of persons and damage at property, when load falls down.

Please check all lifting points carefully before every usage.

 Please check carefully the wear indicator markings of the weld-on lashing point (see pic. 4 and pic. 5):

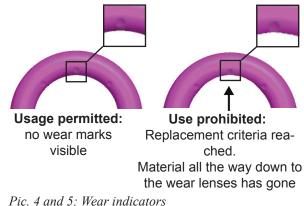

Please note that the lashing mean must be free mo-

- Please note that the lashing mean must be neemoveable in the VRBK-FIX. When lifting means (f.e. lifting chain) are hinged or unhinged, no pinching, shearing or joint spots must occure during the handling.
- Avoid damage of lashing means resulting from sharp edges.
- If RUD-VRBK-FIX lifting points are used solely for lashing, the value of the working load limit can be doubled. LC = permissible lashing force = 2 x working load limit (WLL)

3.5 Hints for regular inspection

In time periods complying to the need or usage, a technical expert must control at least once per year the appropriateness of the lifting point. This inspection must also be done after each event of damage or special incident.

4 Inspection criteria

Observe and control the following points before each initial operation, in regular time intervals, after the assembly and after special incidents:

- · Completeness of the lifting point
- Complete, readable WLL statements as well as manufacturer sign.
- Deformation at load bearing components like base body and ring.
- Mechanical damage, like strong notches, especially in areas where tensile stress occurs.
- Reduction of cross-section due to wear >10 %
- Evidence of corrosion (pittings)
- Evidence of cracks
- Cracks or other damages at weld seam

Method of lift	\$ G1	G	5 5 2xG1	Å G Å	\$8	¢ G	G	G	00	G G
Number of legs	1	1	2	2	2	2	2	3 / 4	3 / 4	3/4
Angle of inclination	0°	90°	0°	90°	0-45°	45-60°	Unsym.	0-45°	45-60°	Unsym.
Factor	1	1	2	2	1.4	1	1	2.1	1.5	1
Туре		For the max. total load weight >G< in metric tons								
VRBK-FIX 4 t	4	4	8	8	5.6	4	4	8.4	6	4
VRBK-FIX 6.7 t	6.7	6.7	13.4	13.4	9.4	6.7	6.7	14	10	6.7
VRBK-FIX 10 t	10	10	20	20	14	10	10	21	15	10
VRBK-FIX 31.5 t	31.5	31.5	63	63	45	31.5	31.5	66.2	47.5	31.5
VRBK 50 t	50	50	100	100	70	50	50	105	75	50

Chart 2: WLL overview

	Europa (DE, GB, FR,) Structural steel, Low alloyed steel	USA, Canada	
MAG / MIG (135) GAS SHIELDED WIRE WELDING	ISO 14341: G4 Si 1 z.B. Castolin 45250	ISO 14341: G4 Si 1 AWS A 5.18 : ER 70 S-6 z.B. Eutectic MIG-Tec A88	HINT Please n
E-Hand Gleichstrom = (111) Stick Electrode Direct Current	EN ISO 2560-A - E 42 6 B 3 2; EN ISO 2560-A - E 38 2 B 12 H10 z.B. Castolin 6666 * Castolin 6666N *	AWS A 5.5 : E 8018-G AWS A 5.5 : E 7016 EN ISO 2560-A - E 42 6 B 3 2; EN ISO 2560-A - E 38 2 B 12 H10; z.B. Eutectic 6666 / 35066 CP*	sponding regard of filler mate drying re
E-Hand ~ Wechselstrom (111) Stick Electrode Alternating Current	EN ISO 2560-A - E 38 0 RR 1 2 EN ISO 2560-A - E 42 0 RR 1 2 z.B. Castolin 6600 / Castolin 35086 no-load-voltage 35-48 (max.) V	AWS A 5.1 : E 6013 EN ISO 2560-A - E 38 0 RR 1 2 EN ISO 2560-A - E 42 0 RR 1 2 z.B. Eutectic Beauty Weld II	*
WIG (141) TIG - Tungsten Arc Welding	ISO 636: W3 Si 1 z.B. Castolin 45255W	ISO 636: W3 Si 1 AWS A 5.18 : ER 70 S-6 z.B. Eutectic TIG-Tec-Tic A 88	


Table 3: Welding procedure + Welding filler metals

Туре	Size	Length	Volume	
VRBK-FIX 4 t	HY 4 + a3	approx. 85 mm	approx. 3.2 cm ³	
VRBK-FIX 6.7 t	HY 5 + a3	approx. 95 mm	approx. 6 cm ³	
VRBK-FIX 10 t	HY 8 + a3	approx. 155 mm	approx. 11 cm ³	
VRBK-FIX 31.5 t	HY 17	approx. 168 mm	approx. 21 cm ³	
VRBK 50 t	HY 25	approx. 227 mm	approx. 61.4 cm ³	



note the correg user hint in f the welding terials and the equirements*.



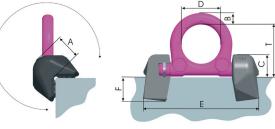

Pic. 4: Dimensioning

Туре	WLL [t]	A [mm]	B [mm]	C [mm]	D [mm]	E [mm]	F [mm]	T [mm]	weight [kg/pc]	RefNo
VRBK-FIX 4 t	4	32	14	28	48	140	29	65	1.0	7902149
VRBK-FIX 6.7 t	6.7	40	20	35	60	180	33	84	2.1	7902150
VRBK-FIX 10 t	10	52	22	46	65	212	46	94	4.4	7902256
VRBK-FIX 31.5 t	31.5	89	42	78	130	394	70	177	24.84	7906225
VRBK 50 t	50	133	70	118	230	626	96	303	76.35	7904653

Table 5: Dimensioning

Table 4: Weld seam (weld-on block)

Subject to technical alterations